

Full Length Research Paper

Fabrication and electrical study of PEM fuel cell based on nano crystalline PEO based conducting polymer electrolyte system

Kambila Vijay Kumar

Centre for Nano Technology, FED, K. L University, Guntur-522 502(A.P), India. E-mail: vijaynanopklu@gmail.com.

Accepted 13 January, 2011

Solid conducting polymer electrolyte system, nano crystalline polyethylene oxide (PEO) complexed with sodium bicarbonate (NaHCO_3) salt was prepared by sol gel-technique. Several experimental techniques such as IR, composition dependence conductivity and temperature dependence conductivity in the temperature range of 303 to 368 K and transport number measurements were employed to characterize this polymer electrolyte system. The conductivity of the (PEO+ NaHCO_3) electrolyte was found to be about 3 times larger than that of pure PEO at room temperature. The transference data indicated that the charge transport in these polymer electrolyte systems is predominantly due to Na^+ . Using this nano crystalline polymer electrolyte system, a three PEM fuel cell stack have been fabricated and their open circuit voltage and I-V characteristics were studied for various gas concentrations. The open circuit voltage was found to be 1.10 V. A number of other cell parameters associated with the cell were evaluated and are reported in this paper.

Key words: Complex, conducting polymer electrolyte, ionic conductivity, transport number, polymer electrolyte membrane (PEM) fuel cell, current-voltage characteristics.

INTRODUCTION

The two primary concerns of scientists today are energy and environment with the rapid depletion of fossil fuels. There is an urgent need to look for clean alternate source of energy. Fuel cells satisfy both these criteria. It is high time that we realize the need for cutting edge technologies which satisfy both conditions, that is, being able to match the present day demand and also being reliable. One such convincing technology is "Fuel cell technology". The necessity for this technology has been widely accepted globally in the energy and power sectors of the many emerging technologies such as biomass fuels, liquid-bio fuels, geothermal energy, Photo-voltaic, hydro-electric power, solar thermal-electricity, tidal-energy, wind-energy, fuel cell technology has been much considered comparative with other technologies and if developed, has more advantages because it has the practicability of being used in many mobile applications and hence this seems to be the futuristic technology

(Sossina et al., 2003). Solid polymer electrolyte membrane fuel cells are promising candidates as power generators for zero emission vehicles in place of conventional combustion engines. These cells use polymer electrolyte membrane (PEM) such as nafion as electrolyte. At present, conducting nano crystalline crystalline polyethylene oxide (PEO) complexed with sodium bicarbonate based PEM are fairly developed/fabricated and have been successfully used in H_2/O_2 , fuel cell. Solid electrolyte PEM requires water to maintain their ionic conductivity. The absorption, diffusion coefficient and electro-osmotic drag of water and proton/ionic conductivity in PEMs and inter related and strongly affected by the cell operating conditions (Yeo, 1983; Verbrugge and Hill, 1990; Bernardi, 1990; Dahr, 1994; Apple and Foulkes, 1989). This problem gets aggregated when the fuel cell is operated at higher temperature (above 70°C) water content in PEM

developed so far has been indirectly managed by humidifying the reactant gases. The electrochemical performance of polymer electrolytes has been improved by the addition of inorganic fillers (Blomen, 1994). The resulting composite polymer electrolytes discharged enhanced conductivity, mechanical stability and improved interfacial stability towards electrode materials (Berers et al., 1997; Andrew and Larwine, Vishnu et al., 2003; Elroy and Nuttall, 2001).

In recent years, an attempt to investigate the possibility of fabricating PEM fuel cell based on other polymer electrolytes (Berers et al., 1997). Some researchers studied and reported on polymer electrolyte membrane fuel cells based on nafion/nafion + silica + phosphotungstic (Sossina et al., 2003) etc. The present work examines a new conducting polymer electrolyte system, namely nano crystalline PEO based ion conducting polymer electrolyte system, that is, PEO+NaHCO₃. Using this solid electrolyte, a PEM fuel cell stack has been fabricated and its i-v characteristics studied.

EXPERIMENTALS

Polymer films (thickness \cong 100 to 150 μm) of pure PEO (Aldrich $\sim 6 \times 10^5$) and various compositions of complexed film of nano crystalline PEO with NaHCO₃ salt was prepared in wt. ratios (90:10); (80:20) and (70:30) by a sol-gel technique using methanol (water free) as solvent. The infrared (IR) spectra in these films have been recorded with the help of JASCO FT / IR-53000-spectrophotometer in the range 400 to 4000 cm^{-1} . The dc conductivity has been measured using the lab made conductivity setup (Sreepathi et al., 1995) in the temperature range 303 to 368 K using a Keithley electrometer (Model 614).

Solid state polymer electrolyte membrane (PEM) fuel cell stack was fabricated in the configuration electrode /solid polymer electrolyte / cathode. The readings were taken with the high purity cylinder gases and the specification design of the PEM fuel cells was reported. The details about the fabrication of the fuel cells are given elsewhere (Elroy and Nuttall, 2001; Swarna and Shyam, 2003; Rai, 2002). Finally the I-V characteristics of these fuel cells were monitored for a constant load of 0.5 Ω .

RESULTS AND DISCUSSION

The variation in dc conductivity (σ) as a function of NaHCO₃ composition in PEO at room temperature (R_T) that is, 303 and 368 K are given in Figure 1. The conductivity of pure PEO is approximately $10^{-10} \text{ Scm}^{-1}$ at room temperature and its value increases sharply to 10^{-7} Scm^{-1} on complexing with 10 wt% NaHCO₃. The increase in conductivity becomes slower on further addition of NaHCO₃ to the polymer. This behavior has been explained by various researchers, who have studied

PVP and PEO based polymer electrolyte in terms of ion association and the formation of charge multipliers (Srivastava et al., 1992; Yuankang and Zhusheng, 1986; Scrosati, 1988; Reddy and Rao, 1998; Chabagno and Duclot, 1979; Narasaiah et al., 1995; Stevens and Mellander, 1987)

The complex of the polymer PEO and salt NaHCO₃ were confirmed by using IR spectroscopy. The IR spectra of pure PEO, PEO complexed with NaHCO₃ were recorded with the help of JASCO FT/IR-5300 spectrophotometer in the range 400 to 4000 cm^{-1} and are shown in Figure 2. The intensity of the aliphatic C-H stretching vibrations band observed around 2950 cm^{-1} in PEO was found to decrease with the increase in the concentration of NaHCO₃ salt in the polymer. The width of the C-O stretching band observed at around 1100 cm^{-1} in PEO also showed an increase in the salt concentration in the polymer. Also the appearance of new peaks along with changes in existing peaks (and/or their disappearance) in the IR-spectra directly indicates the complexation of PEO with NaHCO₃. This IR data clearly establishes the complexation of NaHCO₃ with different weight ratios of the polymer PEO.

The variation in conductivity as a function of temperature for pure PEO with different compositions of (PEO + NaHCO₃) polymer electrolytes over the temperature range of 303 to 368 K is shown in Figure 3. The conductivity versus temperature ($\log \sigma T$ versus $10^3/T$) plots follows the Arrhenius nature throughout, but with two different activation energies (Table 1) above and below melting point (T_m) of the polymer. In region- I (that is, below T_m), the conductivity of pure PEO increases slowly with temperature up to 65°C. At 65°C, there is a sudden increase in conductivity. In region- II (that is, above T_m), the conductivity again increases with temperature. The calculated conductivity (σ) at room temperature, at 368 K and activation energies (E_a) for pure PEO and (PEO+NaHCO₃) electrolyte systems are given in Table 1. The conductivity of pure PEO is $\sim 6.78 \times 10^{-8} \text{ Scm}^{-1}$ at room temperature and its value increases sharply to $\sim 10^{-7} \text{ Scm}^{-1}$ on complexing with 10 wt % of NaHCO₃. The increase in conductivity becomes slower on further addition of NaHCO₃ to the polymer. This behavior has been explained by various researchers, who have studied PMMA and PEO-based polymer electrolyte, interims of ion association and formation of charge multiples (Ramalingaiah et al., 1996; Scrosati, 1988; Hashmi et al., 1992; Sreepathi et al., 1994, 2000). The conductivity increases with temperature in pure PEO and in all the compositions of the (PEO+NaHCO₃) polymer electrolyte system. The ionic conductivity in the polymer complexes may be interpreted on the basis of a hopping mechanism between coordinating sites, local

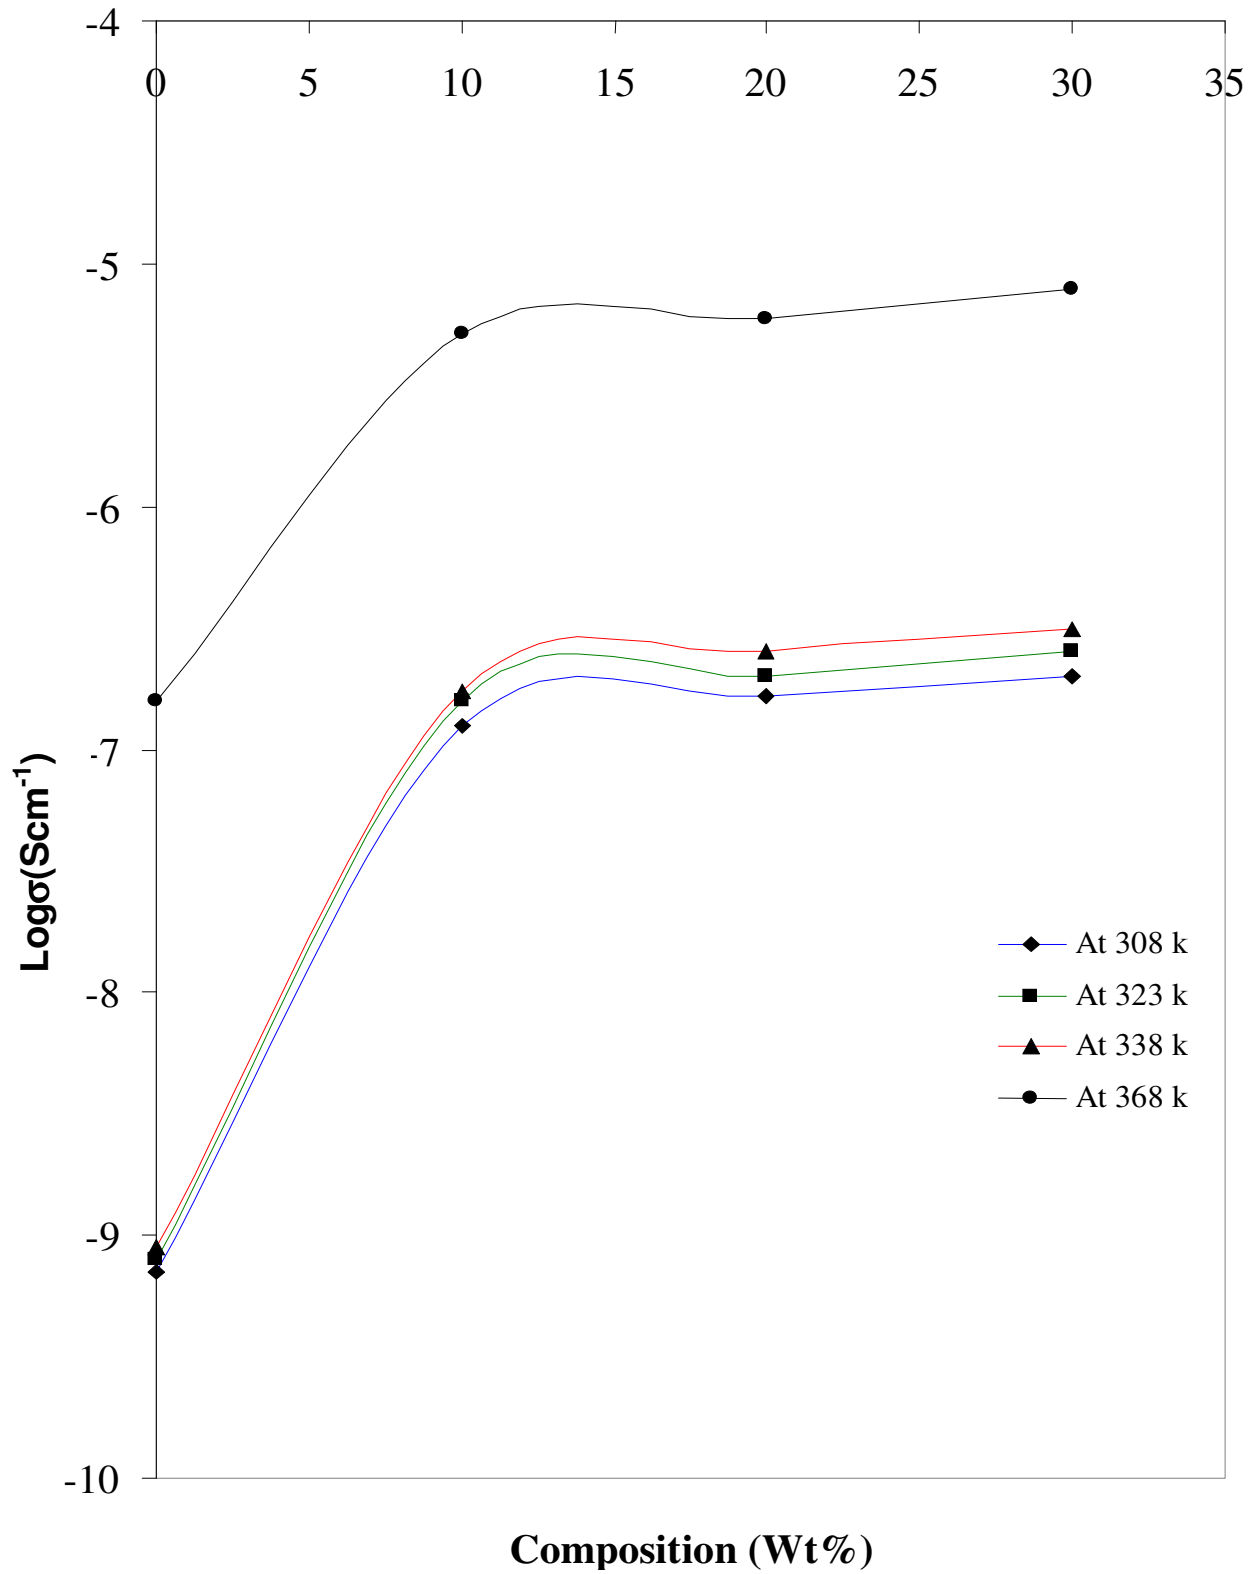


Figure 1. Concentration dependence of $(\text{PEO} + \text{NaHCO}_3)$.

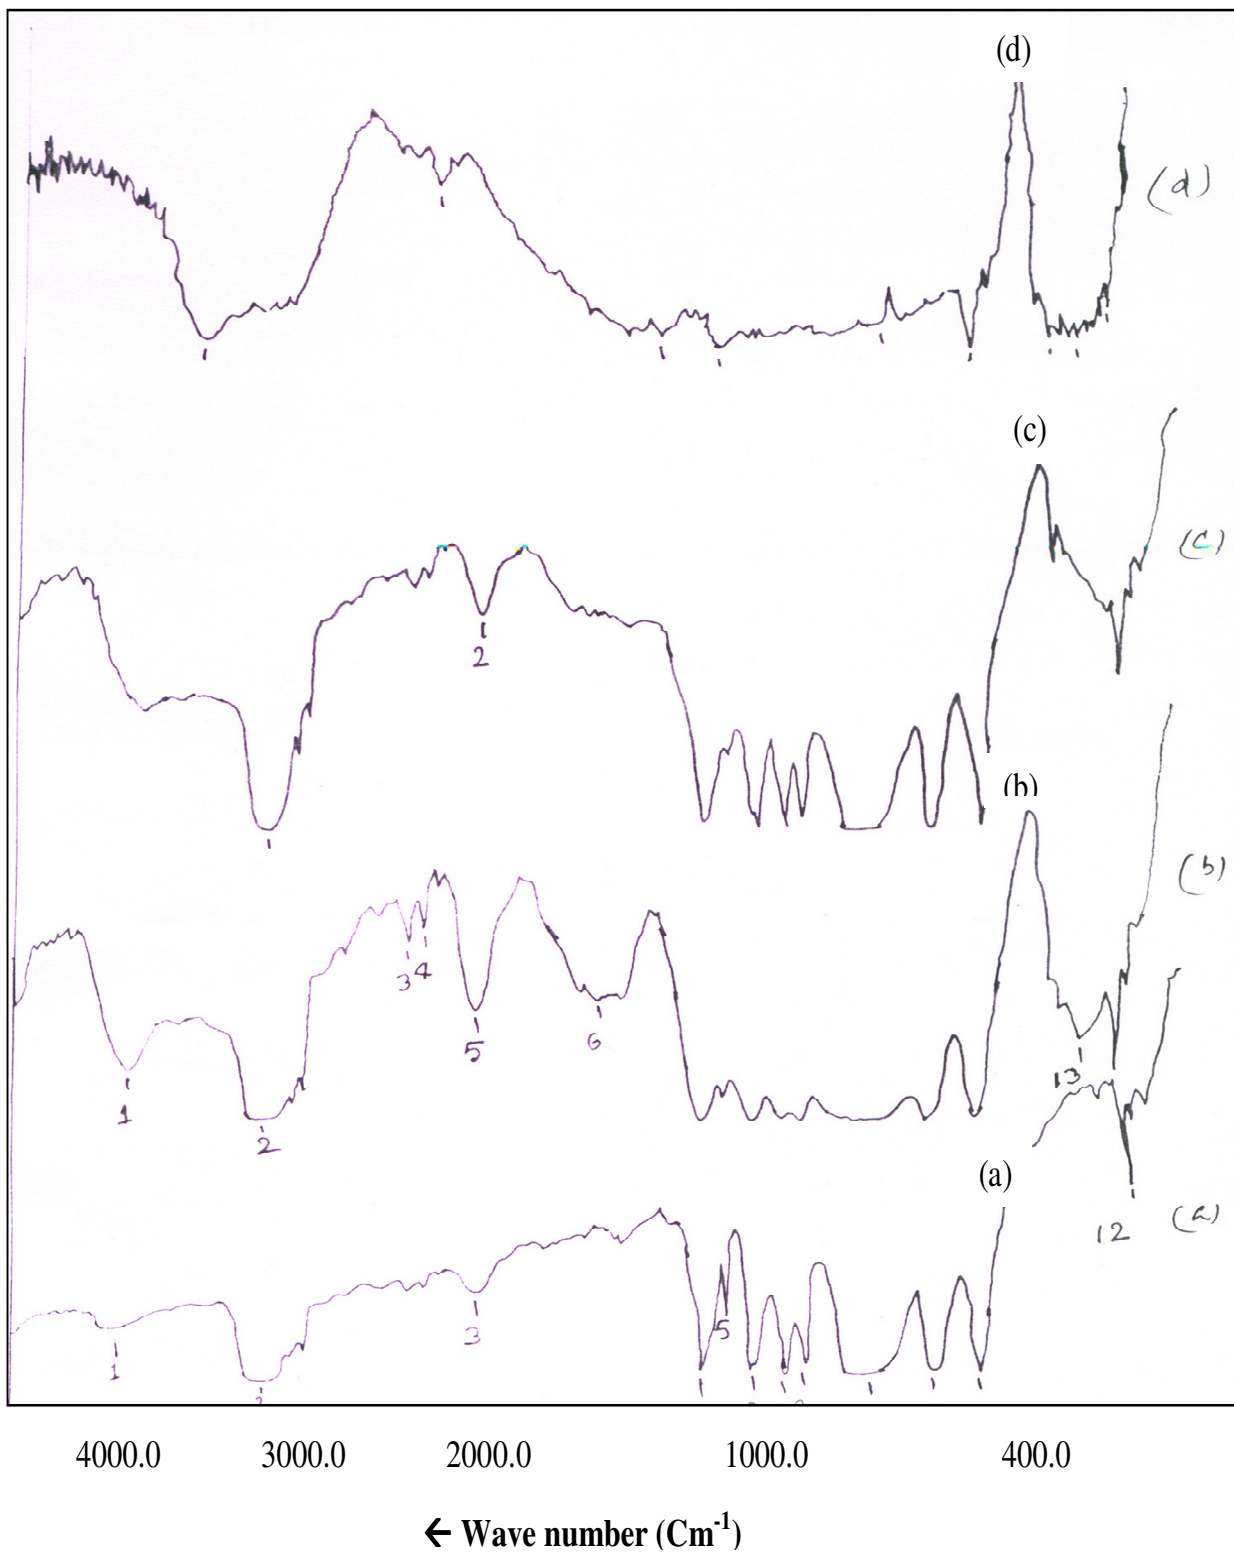


Figure 2. IR-spectra of (a) pure PEO; (b) PEO + NaHCO_3 (90:10); (c) PEO+ NaHCO_3 (70:30), and (d) NaHCO_3 .

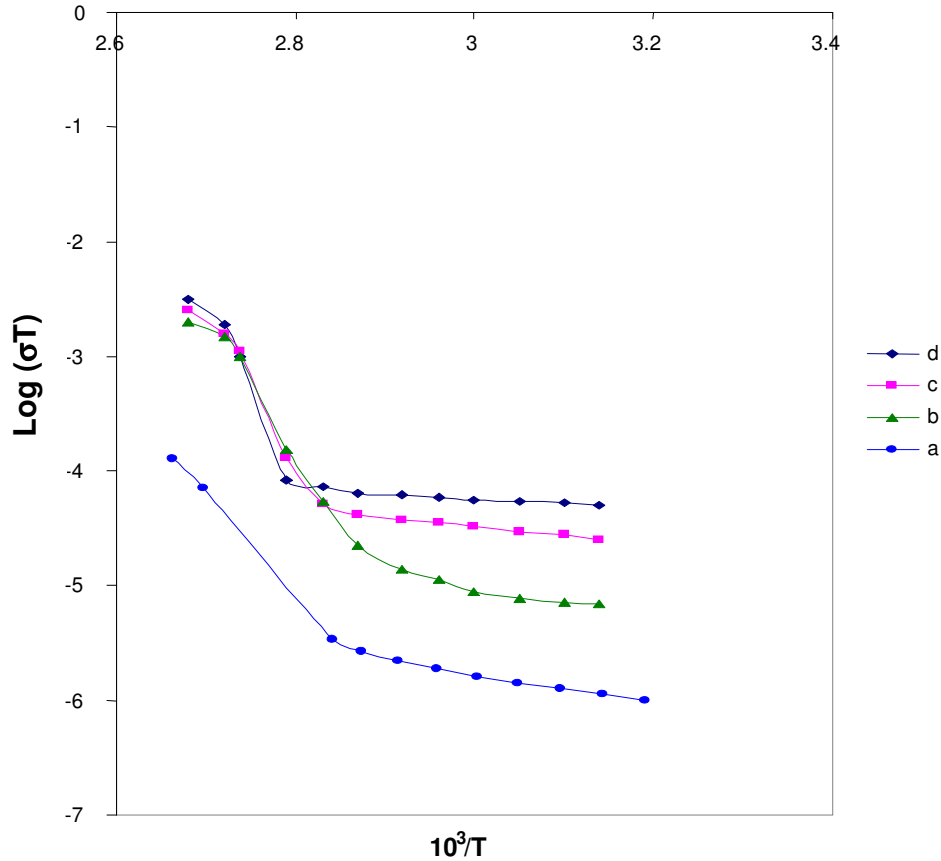


Figure 3. The temperature dependence of D.C. conductivity (a) pure PEO, (b) PEO + NaHCO₃ (90:10); (c) PEO + NaHCO₃ (80:20), and (d) PEO + NaHCO₃ (70:30).

Table 1. D. C. conductivity and activation energies of (PEO + NaHCO₃) electrolyte system.

Film	Conductivity at 303 K (R _T) (Scm ⁻¹)	Conductivity at 368 K (Scm ⁻¹)	Activation energies (eV)	
			Region-I	Region -II
Pure PEO	6.78×10^{-10}	1.58×10^{-7}	0.34	0.59
(PEO + NaHCO ₃) (90:10)	1.55×10^{-7}	5.11×10^{-6}	0.32	0.48
(PEO + NaHCO ₃) (80:20)	1.62×10^{-7}	5.91×10^{-6}	0.25	0.33
(PEO + NaHCO ₃) (70:30)	1.65×10^{-7}	6.33×10^{-6}	0.19	0.28

structural relaxations and segmental motions of the polymer chains; these are essential to assure high ionic conductivity of the electrolyte (Sreepathi et al., 1994, 2000; Vijaya et al., 2007). The basic design of the cell, which consists of a solid electrolyte ion-exchange membrane, electro catalysts and gas feed fuels is illustrated in Figure 4.

The two electrodes, which consist of the electro catalyst and a plastic material for water-proofing the

electrode, are in the form of fine metallic wire screens. They are bonded on either side of the electrolyte layer. The wire screen material is titanium or platinum. Metallic current collectors are ribbed onto each electrode. The hydrogen compartment of the cell is enclosed; the hydrogen gas enters this compartment through a small inlet and circulates throughout the ribbed current collectors and distributes itself evenly over the electrode. On the opposite side, oxygen or air enters the


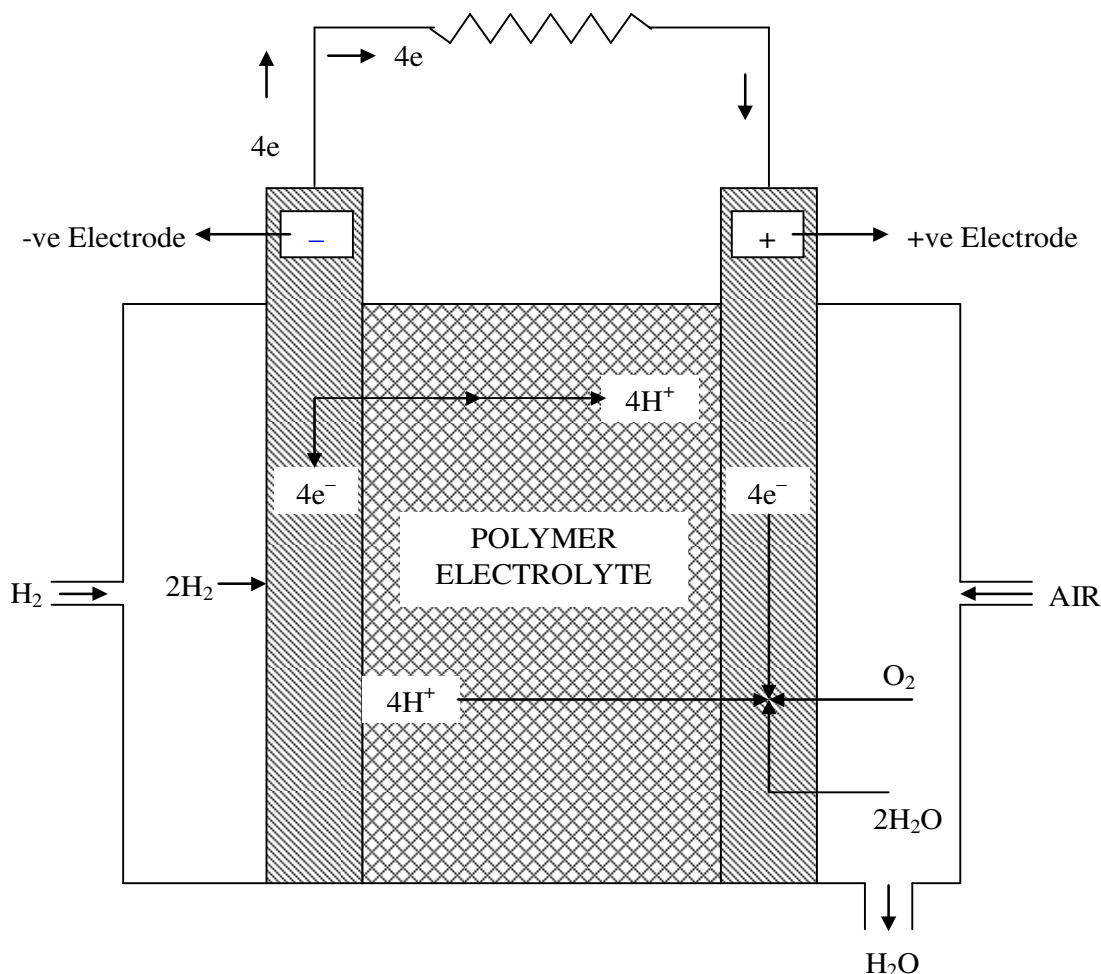


Figure 4. Polymer electrolyte membrane fuel cell (PEMFC).


compartment, coolant tubes run through the ribs of the current collectors. On the oxygen side, the current collectors also hold wicks which absorb water, the product of fuel-cell reaction and carry it over by capillary action. The water leaves the cell through an exit from the oxygen compartment. Oxygen is prevented from leaving its compartment by the inclusion of a differential pressure water-separation system. The distinctive feature of this cell is that it uses a solid polymer electrolyte in the form of an ion-exchange membrane. The membrane is non-permeable to the reactant gases, hydrogen and oxygen, which thus prevents them from coming into contact. The membrane is however; permeable to hydrogen ions (Vishnu et al., 2003) which are the current carriers in the electrolyte. The desired properties of polymer electrolyte membrane are high ionic conductivity, low permeability of fuel and oxidant, very low electronic conductivity, high resistance to its oxidation or hydrolysis and mechanical

stability (Proceedings from 3rd International Fuel Cell Conference, Nagoya Tuting, Nov. 30th to Dec 3rd 1999, Japan).

The ion-exchange membrane electrolyte is acidic and the current carriers in solution are hydrogen ions. The hydrogen ions are produced by the reaction at anode according to,



These ions are then transported to the cathode through the electrolyte and the electrons reach the cathode via the external circuit. At the cathode, oxygen is reduced producing water as represented by:



This cell operates at about 40 to 70°C. The single cell1

Table 2. Specifications for single cell 1.

Electrode	20% carbon anode and cathode
Polymer electrolyte	(PEO+NaHCO ₃) (90:10)
Type of graphite rates	Porous 1 no. and non-porous 1 no.
Concentrating NaBH ₄	10%
Fuel	H ₂ and O ₂ (from cylinders)

Table 3. Specifications for single cell 2.

Electrode	20% carbon anode and cathode
Polymer electrolyte	(PEO + NaHCO ₃) (80:20)
Type of graphite rates	Porous 1 no. and non-porous 1 no.
Concentrating NaBH ₄	15%
Fuel	H ₂ and O ₂ (from cylinders)

Table 4. Specifications for cell 3.

Electrode	20% carbon anode and cathode
Polymer electrolyte	(PEO+NaHCO ₃) (70:30)
Type of graphite rates	Porous 1 no. and non-porous 1 no.
Concentrating NaBH ₄	20%
Fuel	H ₂ and O ₂ (from cylinders)

Table 5. Specifications for the three PEM fuel cells stack.

Electrode	20% carbon electrodes no. 6
Electrolytes	PEO + NaHCO ₃ (90:10) PEO + NaHCO ₃ (80:20) PEO + NaHCO ₃ (70:30)
Electrolyte chamber thickness	4 mm (3)
Electrolyte temperature	65 °C
Graphite plates	Non-porous (4) Mono-polar - 2 no. Bi-polar – 2 no.
Concentration of sodium borohydride	30%
Hydrogen and oxygen	Completely running on cylinder Gases

with the configuration anode / (PEO+NaHCO₃) (90:10)/ cathode was assembled with the specifications and the first readings were taken with the cylinder gases. The specifications of the single fuel cell with the polymer electrolyte are given in Table 2. The resistor, 0.5 Ω were added in series to the circuit to gain an increase in voltage. Subsequently it was achieved. The open circuit voltage was found to be 0.95 V.

The single cell 2 and single cell 3 with the configurations anode/(PEO+NaHCO₃) (80:20)/ cathode and anode/(PEO+NaHCO₃) (70:30) (Tables 3 and 4) were assembled with the specifications. The specification design of the PEM fuel cell2, cell3 was given in Tables 3 and 4, respectively. The observations were taken with the cylinder gases. The resistor 0.5 Ω was connected in series to the circuit. It is observed that, when the cell current increases, cell voltage slightly decreases (Proceedings from 3rd International Fuel Cell Conference, Nagoya Tuting, Nov. 30th to Dec 3rd 1999, Japan) up to 0.61 V due to concentration of sodium borohydride.

After testing successfully with the single cell, a three cell stack was assembled (that is, the three single cells are connected in series). The material require for this assembly is similar to that of the single cell. But the quantity of the material is increased. The material required for assembly and its quantity is given in Table 5.

For the three cell stack, we used non-porous, bi-porous graphite plates. The three design aspects of the PEM fuel cell system under fabrication are (1) the hydrogen on demand generation system (that is, hydrogen reformer system) and (2) the air scrubber system (that is, the fuel cell assembly). The incorporation of the aforementioned three designs completes the fuel cell system (Stomehart, 1996). Using this conducting polymer electrolyte thin film systems, a three fuel cell stack have been fabricated and I-V characteristics studied and the results were subsequently summarized.

The basic design of the cell consists of a solid polymer electrolyte ion-exchange membrane, electro catalysts and gas fuel tubes. Hydrogen was generated from sodium borohydride (NaBH₄) and air was scrubbed using the initial setup of the air scrubber. The fuel cell system was run completely on generated gases. The distinctive feature of this cell is that it uses a solid electrolyte in the form of an ion-exchange membrane. The membrane is non-permeable to the reactant gases hydrogen and oxygen, which thus prevents them from coming into contact. The membrane is however, permeable to hydrogen ions (Journal of Industry Report, Global News on the Advances and Applications of the Fuel Cell Technology, Dec. 2000, Vol. 1, No. 12) which are the current carriers in the polymer electrolyte. This cell operates at around 40 to 70 °C.

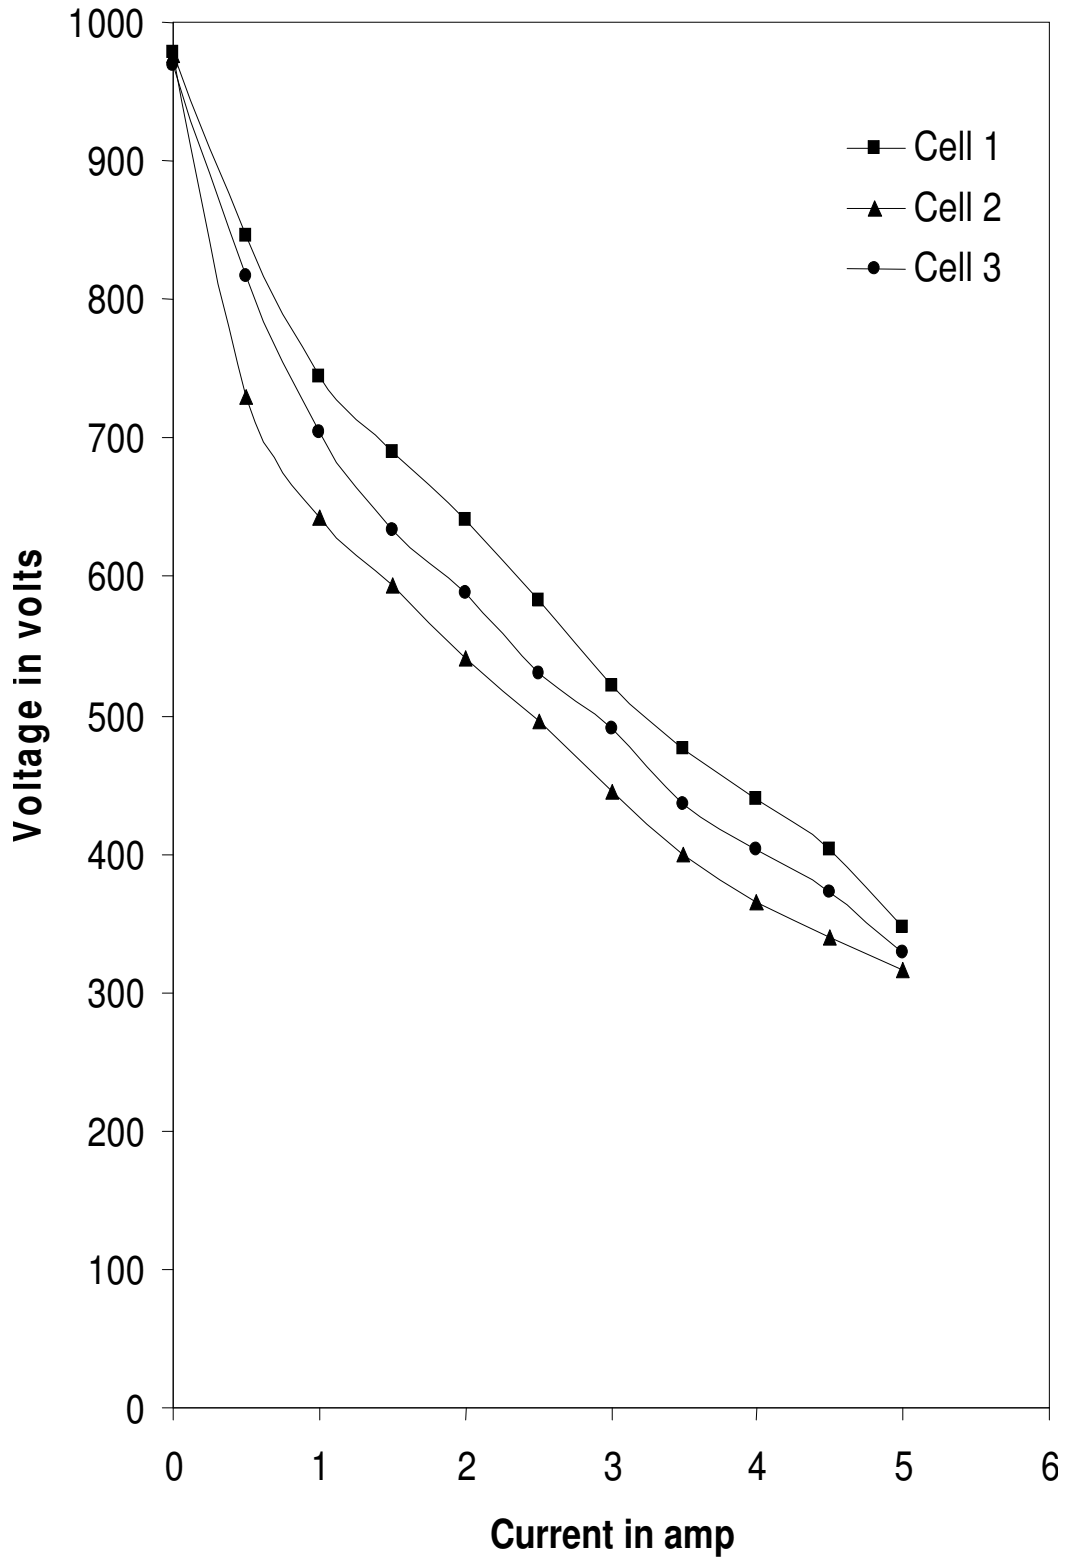


Figure 5. I-V Characteristics of a single cell 1, 2 and 3 of a (PEO + NaHO₃) based PEM fuel cell.

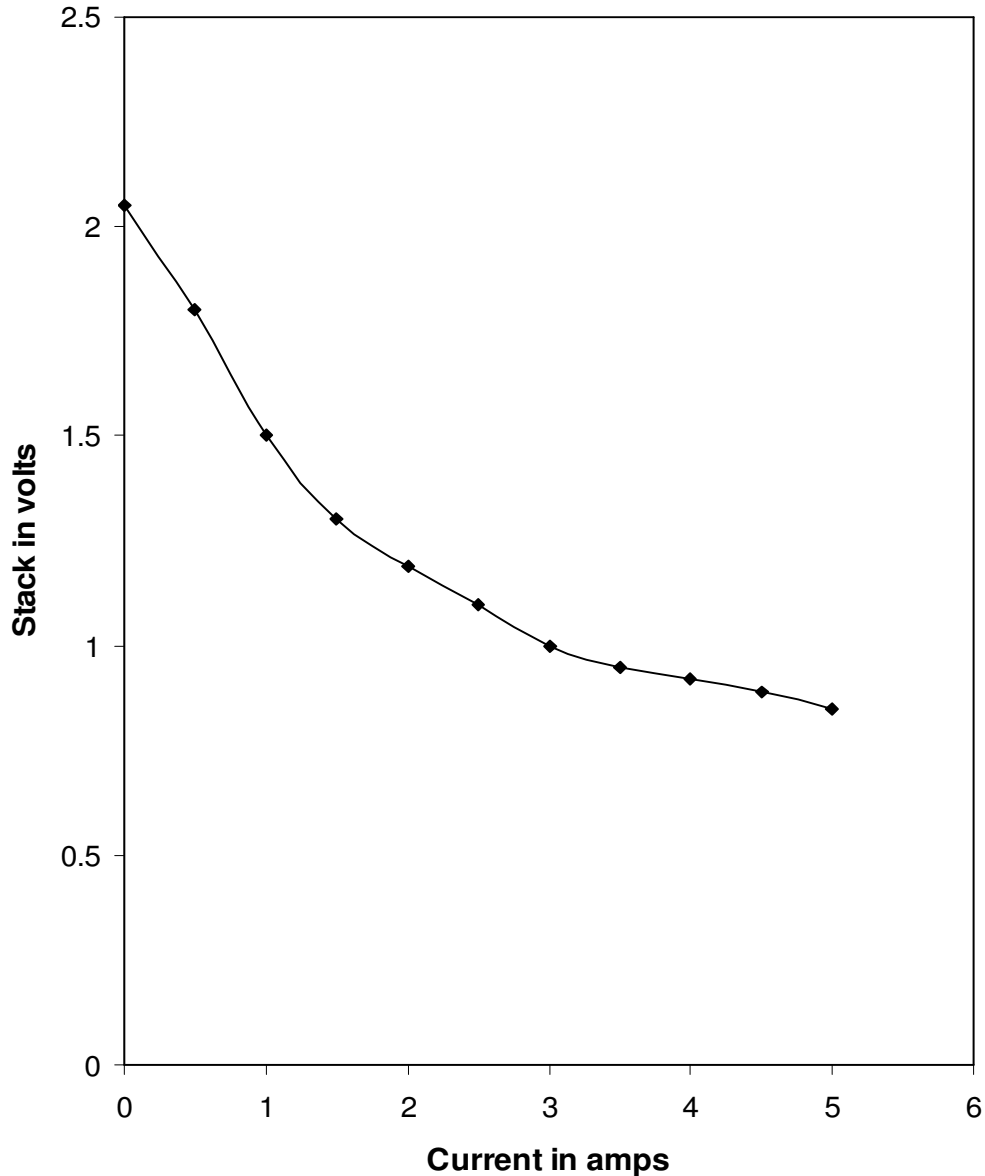


Figure 6. I to V characteristics of a three PEM fuel cell stack.

Polymer electrolyte fuel cells are assembled in the configuration (anode) / (polymer electrolyte) / (Cathode) and their I-V characteristics was studied. The main function of the electrolyte in PEMFC is to carry the O^{2-} from the cathode to the anode and also it separates the fuel from the oxidant inside the cell. The high ionic electrolytes are independent of oxygen partial pressure. In PEMFC the (PEO+NaHCO₃) electrolyte system is typically chosen as the base line material. And also most of the polymer electrolyte systems have good mechanical strength, fracture toughness, better ionic conductivity and

lesser chemical reactivity with the cathode, anode and inter connectors (Proceedings from 3rd International Fuel Cell Conference, Nagoya Tuting, Nov. 30th to Dec 3rd 1999, Japan).

The current voltage characteristics of the single cell1, single cell2 and single cell3 are shown in Figure 5. From the figure, it is observed that, when current of the cell increases, the developed voltage of the cell gradually decreases.

The three fuel cell stack, and I-V characteristics were also studied and it is shown in Figure 6. The voltage of

the fuel cell stack gradually decreases with increase in current. The open circuit voltage of these fuel cells has been measured for different compositions of various polymer electrolyte systems. It is observed that the open circuit voltage was found to be in range 0.95 to 1.1 V. it may be due to used electrolyte membrane type, electro catalysts and concentration of sodium borohydride.

Conclusion

1. The fuel cell stack is found to be better performance as compared to a single cell fuel cell.
2. (PEO+NaHCO₃) three cell stack wattage is found to be 4.25 watt with a stack voltage of 0.85 V. The fuel cell characteristics like I-V characteristics, open circuit voltage, power density etc. mainly depends on nature of electrolyte, the generated gases and its purity. But it is observed that the volt-ampere characteristics, efficiency of these fuel cells are very low. Further work has to be done to improve the fuel cell efficiency by proper choosing of solid polymer electrolytes along with the electrodes.
3. The improve power density, current density of the fuel cell mainly depends on the nature of catalyst used in the fabrication. Among all the electrodes, platinum is a very good catalyst but, its cost is very high. Therefore studies of other catalyst materials in the place of platinum are needed.

ACKNOWLEDGEMENTS

The author thanks Er. Koneru Satyanrayana, Chancellor, K. L. University Guntur (A.P) for his encouragement and support and also the author is highly grateful to Dr. G. L. Datta, Vice Chancellor K. L. University. Finally, the author thanks Prof. N. Venkat Ram, Dean, F. E. D and Department of Physics, K L University for his constant support.

REFERENCES

- Andrew W, James L (2003). Fuel cell systems explained. John Wiley and Sons, Ltd., ISBN No. 0-471-49026-1.
- Apple AJ, Foulkes FR (1989). Fuel cell Handbook. Van Nostrand Reinhold, New York, USA.
- Berens D, Wagner N, Von Bradke M, (1997). Int. Hydrogen Energy., 23: 57.
- Bernardi DM (1990). Electrochemical modelling of lead/acid batteries under operating conditions of electric vehicles. J. Electrochem. Soc., 137: 3344.
- Blomen LT (1994). Fuel cell systems, Plenum Publishing Corporation, New York.
- Chabagno JM, MJ Duclot (1979). Fast Ion transport in Solids. Vashista P, Mundy JN, Shenoy GK, Eds., North Holland, New York, p. 131.
- Dahr HP (1994). Perfluorinated Ionic Polymers for PEFCs (Including Supported PFSA). Fuel Cell Semin., p. 85.
- Elroy JFMC, Nuttall LJ (2001). Status of solid polymer electrolyte fuel cell technology and potential for transport and applications by General Electric company, Direct energy conversions programmes.
- Hashmi SA, Chandra A, Chandra S, Chowdari BVR (1992). Solid State Ionics: Materials and Application World Scientific, Singapore, p. 567
- Narasaiah EL (1995). Study of a new polymer electrolyte (PVP+KYF4) for solid-state electrochemical cells." J. Power Source, 55: 255-257.
- Proceedings from 3rd International Fuel cell conference, Nagoya Tuting, Nov. 30th to Dec 3rd (1999), Japan.
- Rai GD (2002). Non-conventional Energy sources. Khanna Publishers, New Delhi, pp. 561-589.
- Ramalingaiah S, Reddy DS (1996). Conductivity and discharge characteristic studies of novel Polymer electrolyte based on PEO complexed with Mg(NO₃) salt. Mater. Lett., 29: 285-289.
- Reddy MJ, Rao UVS (1998). Transport Studies of Poly (ethylene oxide) based polymer.
- Scrosati B (1988). Solid state Ionic Devices." Edited by Chodary BVR, Radha S, Krishna, World Scientific Publishing Co., Singapore, p. 113.
- Sossina M, Haile F (2003). Materials for Fuel Cells. Mater. Today.
- Sreekanth T, Jaipal Reddy M, Subba RUV (2000). Polymer electrolyte system based on (PEO+KBrO₃) - Its application as an electrochemical cell. J. Power Sources, 3994: 1-5.
- Sreepathi R, Jaipal SR, Laxmi NM, Subba RUV (1995). Polymer electrolyte system based on (PEO+KBrO₃)-its application as an electrochemical cell. Mat. Sci. Eng., 33: 173.
- Sreepathi RS, Rao KVS, Shareefuddin UV, Subba R, Chandra S (1994). 'Ionic Conductivity and battery characteristic studies on PEO+AgNO₃ polymer electrolyte." Solid State Ion., 67: 331-334S.
- Srivastava PC (1992). Solid-state Ionics: Materials and Applications, Edited by Chowdari BVR, World Scientific, Singapore, pp. 561-565.
- Stevens JR, Mellander BR, (1987). Conducting Polymers. Edited by Alcacer L, Reidel, Dordrecht, p. 95.
- Stomehart P (1996). Polymer-silica composite membranes for direct methanol fuel cells. Proc. Fuel Cell Semin., p. 591.
- Swarna R, Shyam KT (2003). Thesis – Design and fabrication of alkaline fuel cell stack.
- Verbrugge MW, Hill RF (1990). Radiotracer method for simultaneous measurement of cation, anion and water transport through ion-exchange membranes. J. Electrochem. Soc., 137: 886.
- Vijaya K, Venkata R, Reddy CH (2007). Characterization and electrical studies of polyethylene oxide based thin film polymer electrolytes.' Int. J. Acta Ciencia Indica, 37(4): 473.
- Vishnu PB, Jai S, Prakash, Ramya K, Dhathathreyan KS (2003). Solid State Ion. Devices Sci. Technol., pp. 118-129.
- Yeo RS (1983). Sorption and transport behavior of perfluorinated ionomer membranes in concentrated NaOH solution. J. Electrochem. Soc., 130: 533.
- Yuankang H, Zhusheng C (1986). Materials for Solid State Ionics. In: Chowdari BVR, Radha KS (Eds), World Scientific, Singapore, p. 333.